



UNIVERSITI PUTRA MALAYSIA

**FATIGUE BEHAVIOUR OF OIL PALM FRUIT BUNCH FIBRE/EPOXY
AND CARBON FIBRE/EPOXY COMPOSITES**

ANIZAH KALAM

FK 2003 3

**FATIGUE BEHAVIOUR OF OIL PALM FRUIT BUNCH FIBRE/EPOXY
AND CARBON FIBRE/EPOXY COMPOSITES**

By

ANIZAH KALAM

**Thesis Submitted to the school of Graduate Studies, Universiti Putra Malaysia,
in Fulfilment of the Requirement for the Degree of Master of Science**

April 2003



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in partial fulfilment of the requirements for the degree of Master of Science

**FATIGUE BEHAVIOUR OF OIL PALM FRUIT BUNCH FIBRE/EPOXY
AND CARBON FIBRE/EPOXY COMPOSITES**

By

ANIZAH KALAM

April 2003

Chairman: Professor Ir. Dr. Barkawi Bin Sahari

Faculty : Engineering

Tensile test on unidirectional Oil Palm Fruit Bunch (OPFB) fibre/epoxy composite and unidirectional Carbon Fibre (CF)/epoxy composite were conducted to determine their ultimate tensile stress, the Young's modulus and elongation at fracture. Two different fibre volume fractions of 35% and 55% were studied in OPFB fibre/epoxy composite. The fibre volume fraction of CF/epoxy composite studied was 42%. The ultimate tensile stress determined from the tensile tests were then used to determine the maximum stress levels, S_{max} of fatigue tests for CF and OPFB fibre/epoxy composites.

Two parameters were studied in fatigue test, which were stress ratio, R (0.1 and 0.5) and fibre volume fraction, V_f (35% and 55%). All Fatigue tests were performed at constant stress amplitude, at an air-conditioned room temperature of 20°C and at a frequency of 20 Hz. Observation on fractured surface of tensile and fatigue tested specimens were also done.

The ultimate tensile stress of CF/epoxy composite is 247.0 MPa. OPFB fibre/epoxy composite with fibre volume fraction of 35% and 55% have ultimate tensile stress of 47.8 MPa and 46.1 Mpa, respectively.

The observation on fractured surface of tensile tested specimens showed that CF and OPFB fibre/epoxy composites failed in a brittle manner. Fatigue behaviour of CF/epoxy composite shows a reduction in fatigue resistance with decreasing stress ratio. Three specimens survived 1 million cycles, which were cycled at stress ratio of 0.1 and maximum stress level, S_{max} of 0.65. There was no indication of fatigue limit shown by S-N curves for OPFB fibre/epoxy composite for both fibre volume fractions. However the S-N curves of OPFB fibre/epoxy composite showed a decrease of fatigue resistance with the increase of fibre volume fraction from 35% to 55%.

Two types of fractured surface were observed on the CF/epoxy composite failed in fatigue test, which were brittle and delamination. Meanwhile the fractured surface of OPFB fibre/epoxy composite showed brittle, delamination and fibre pull-out.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia
sebagai memenuhi sebahagian dari keperluan untuk ijazah Master Sains

**KELAKUAN LESU BAGI KOMPOSIT SERAT TANDAN KELAPA
SAWIT/EPOXY DAN KOMPOSIT SERAT KARBON/EPOXY**

Oleh

ANIZAH KALAM

April 2003

Pengerusi: Profesor Ir. Dr. Barkawi Bin Sahari

Fakulti : Kejuruteraan

Ujian tegangan telah dijalankan keatas komposit berserat searah dari tandan kelapa sawit (OPFB)/epoxy dan serat karbon (CF)/epoxy untuk menentukan tegasan tegangan muktamad, modulus Young dan pemanjangan pada masa patah. Bahan komposit OPFB/epoxy yang dikaji mempunyai pecahan isipadu serat yang berbeza iaitu 35% dan 55%. Manakala pecahan isipadu serat bagi komposit CF/epoxy adalah 42%. Tegasan tegangan muktamad yang telah didapati dari ujian tegangan akan digunakan untuk menentukan paras tegasan maksima yang dikenakan dalam ujian kelesuan bagi kedua-dua komposit.

Dua parameter yang dikaji dalam ujian kelesuan adalah nisbah tegasan, R (0.1 dan 0.5) dan juga pecahan isipadu serat, V_f (35% dan 55%). Semua ujian kelesuan dijalankan pada amplitud tegasan yang malar, di dalam bilik berpendingin hawa pada suhu 20°C dan frekuensi 20 Hz. Pemerhatian ke atas bahagian permukaan spesimen yang patah dalam ujian tegangan dan ujian kelesuan juga dilakukan.

Nilai tegasan tegangan muktamad yang didapati dari ujian tegangan bagi komposit CF/epoxy adalah 247.0 MPa. Manakala komposit OPFB fibre/epoxy yang mempunyai pecahan isipadu serat 35% dan 55% masing-masing menunjukkan nilai tegasan tegangan muktamad 47.8 MPa dan 46.1 MPa.

Pemerhatian keatas bahagian permukaan yang patah dalam ujian tegangan menunjukkan komposit CF/epoxy dan OPFB/epoxy patah secara rapuh. Kelakuan kelesuan bagi komposit CF/epoxy menunjukkan pengurangan dalam rintangan kelesuan terhadap penurunan nisbah tegasan. Tiga spesimen yang dikitar pada nisbah tegasan 0.1 dan paras tegasan maksimum 0.65 telah bertahan tanpa patah sehingga 1 juta kitaran. Tiada tanda had kelesuan ditunjukkan oleh lengkuk S-N bagi kedua-dua komposit OPFB/epoxy. Walaubagaimanapun lengkuk S-N bagi komposit OPFB/epoxy menunjukkan pengurangan rintangan kelesuan terhadap pertambahan pecahan isipadu serat dari 35% ke 55%.

Komposit CF/epoxy yang patah dalam ujian kelesuan menunjukkan dua jenis permukaan patah iaitu secara rapuh dan sedikit tanda penyahlapisan. Manakala komposit OPFB/epoxy menunjukkan permukaan patah secara rapuh, sedikit penyahlapisan dan juga lolosan serat.

ACKNOWLEDGEMENTS

Through the completion of the project many people have helped in its development and I would like to acknowledge their valued suggestions and comments. Specifically, I wish to express my profound appreciation and gratitude to the chairman of the supervisory committee, Professor Dr. Barkawi Sahari for his supervision, guidance, constructive suggestions, comments and his valuable time spent during the discussion.

A particular note of thanks is also given to the members of the supervisory committee, Associate Professor Dr. Yousif A. Khalid and Dr. Wong Shaw Voon for their guidance, suggestions and comments throughout the duration of the project.

I would also like to thank Tuan Haji Saharani for his technical expertise, guidance and assistance in using the Instron machine to perform the tests for this study. And also my appreciation to Wildan for his assistance during the test was carried out and to Ahmad Saifudin for his help and willingness to give some ideas in preparing the specimen's mould.

Many thanks are also extended to all the friends in Universiti Teknologi MARA and Universiti Putra Malaysia who contributed in giving ideas, suggestions and comments to this project.

Finally, and most importantly, I would like to express my deep gratitude to my husband, my sons and my daughter for their patience, love and full support, which allowed this report to be completed.

I certify that an Examination Committee met on 1st April 2003 to conduct the final examination of Anizah Kalam on her Master of Science thesis entitled “Fatigue Behaviour of Oil Palm Fruit Bunch Fibre/Epoxy and Carbon Fibre/Epoxy Composites” in accordance with the Universiti Pertanian Malaysia (Higher Degree) Act 1980 and Universiti Pertanian Malaysia (Higher Degree) Regulations 1981. The Committee recommends that the candidate be awarded the relevant degree. Members of the Examination Committee are as follows:

Mageed Hamouda, Ph.D.

Associate Professor,
Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia
(Chairman)

Barkawi Sahari, Ph.D.

Professor,
Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia
(Member)

Yousif A. Khalid, Ph.D.

Associate Professor,
Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia
(Member)

Wong Shaw Voon, Ph.D.

Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia
(Member)



GULAM RUSUL RAHMAT ALI, Ph.D.

Professor / Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date **11 April 2003**

This thesis submitted to the Senate of Universiti Putra Malaysia has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisory Committee are as follows:

Barkawi Bin Sahari, Ph.D.

Professor,
Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia.
(Member)

Yousif A. Khalid, Ph.D.

Associate Professor,
Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia.
(Member)

Wong Shaw Voon, Ph.D.

Department of Mechanical and Manufacturing Engineering,
Faculty of Engineering,
Universiti Putra Malaysia.
(Member)




AINI IDERIS, Ph.D.
Professor/Dean,
School of Graduate Studies,
Universiti Putra Malaysia.

Date: **15** AUG 2003

DECLARATION

I hereby declare that the thesis is based on my original work except for quotations and citations, which have been duly acknowledged. I also declare that it has not been previously or concurrently submitted for any other degree at UPM or other institutions.



ANIZAH KALAM

Date: 18/06/03

TABLE OF CONTENTS

	Page
ABSTRACT	ii
ABSTRAK	iv
ACKNOWLEDGEMENTS	vi
APPROVALS	vii
DECLARATION	viii
LIST OF TABLES	xiii
LIST OF FIGURES	xiv
NOMENCLATURE	xvii
 CHAPTER	
1 INTRODUCTION	1
2 LITERATURE REVIEW	11
2.1 General	11
2.2 Behaviour of Unidirectional Composites	12
2.2.1 Factors Which Determine the Properties	14
2.2.2 Longitudinal Strength	15
2.2.3 Young's Modulus	19
2.3 Fatigue Behaviour of Composite Materials	20
2.3.1 Cyclic Stress-strain Behaviour	24
2.3.2 Consequences of Cyclic Loading on the Strength, Stiffness and Life	27
2.4 Failure Mechanism	29
2.5 Fatigue Test Method	32
2.5.1 Load Control	33
2.5.2 Strain Control	34
2.5.3 Fatigue Test Parameters	36
2.6 Empirical Relations for Fatigue Failure	37
2.7 Scatter and Statistical Aspects in Fatigue	39
2.8 Related Previous Work	42
2.8.1 The Effect of Fibre Volume Fraction on Fatigue Performance	42
2.8.2 The Effect of Temperature on Fatigue Life of Composite	43



2.8.3	The Influence of Frequency on Fatigue Life of Composite	45
2.8.4	The Effect of Stacking Sequence and Fibre Orientation on Fatigue Strength	46
2.8.5	Fatigue Behaviour of Polymer-based Composites	48
2.8.6	Relation between Failure Mechanisms and Fatigue Life	52
2.8.7	Tensile Properties of Polypropylene-oil Palm Empty Fruit Bunch-glass Fibre Hybrid Composites	53
2.8.8	Tensile Fatigue Behaviour of Epoxy	56
2.9	Discussion	57
3	METHODOLOGY	58
3.1	Materials Description	58
3.2	Specimen Preparation	59
3.3	Tests Description	62
3.3.1	Tensile Test	63
3.3.2	Fatigue Test	64
3.4	Discussion	66
4	TENSILE TESTS RESULT AND DISCUSSION	67
4.1	Tensile Test Data	67
4.2	Stress-strain Curves	70
4.3	A Comparison of Stress-strain Curves	75
4.4	Discussion	76
5	FATIGUE TESTS RESULT AND DISCUSSION	77
5.1	Fatigue Tests Profile	77
5.2	Fatigue Tests Data for CF/epoxy Composite	79
5.3	The S–N Curves for CF/epoxy Composite	81
5.4	Fatigue Tests Data for OPFB Fibre/epoxy Composite	85
5.5	The S–N Curves for OPFB Fibre/epoxy Composite	88
5.6	A Comparison of Fatigue Behaviour	92
5.7	The Effect of Stress Ratio, R	94
5.8	The Effect of Fibre Volume Fraction, V_f	96
5.9	Observation on Fractured Surface for CF/epoxy Composite Specimens	99
5.10	Observation on Fractured Surface for OPFB Fibre/epoxy Composite Specimens	102

5.11	Discussion	106
6	GENERAL DISCUSSION	107
6.1	Objectives	107
6.2	Fabrication Method	108
6.3	Experimental Work	109
6.4	Test Procedure	110
6.5	Test Results	110
6.6	Sources of Error	111
7	CONCLUSIONS AND RECOMMENDATIONS	112
7.1	Conclusions	112
7.2	Recommendations	116
	REFERENCES	117
	APPENDICES	121
	VITA	135

LIST OF TABLES

Table	Title	Page
2.1	: Constants in S-N representation of composite laminates	38
2.2	: The parameters of K and c for various laminates	39
2.3	: The fatigue test conditions of CFRP at frequency of 50 Hz	44
2.4	: Fatigue properties of CFRP as a function of frequency	46
2.5	: The fatigue test conditions of CFRP at frequency of 50 Hz	47
2.6	: Properties of the materials and static test result	49
2.7	: Mechanical properties of carbon fibre and neat resins	51
2.8	: The proportion of OPFB fibre/glass fibre	54
2.9	: Static properties of the tested specimens	56
3.1	: The properties of OPFB fibre/PP composite	59
3.2	: Particulars of the tested materials	60
3.3	: The particulars for fatigue test of R = 0.1	65
4.1	: Tensile tests result of all the materials tested	68
4.2	: The calculated mean σ_{ult} according to Weibull distribution	69
5.1	: Fatigue tests data for CF/epoxy composite	79
5.2	: The m and b parameters for S-N curves of CF/epoxy composite	83
5.3	: The parameters of K and c for two different stress ratios	85
5.4	: Fatigue tests data for OPFB fibre/epoxy composite	86
5.5	: The m and b parameters of OPFB fibre/epoxy composite	91
5.6	: The K and c parameters of OPFB fibre/epoxy composite	92
5.7	: The m and b parameters for CF/epoxy composite and OPFB fibre/epoxy composite	96
5.8	: The parameters of K and c for CF/epoxy composite and OPFB fibre/epoxy composite	98
7.1	: The elastic properties of the materials tested	110
7.2	: The fatigue constants of the materials tested	112

LIST OF FIGURES

Figure	Title	Page
1.1	: Typical S-N curve fatigue life curve	6
2.1	: Schematic representation of unidirectional composite	12
2.2	: Longitudinal stress-strain diagrams for hypothetical composites	17
2.3	: Stress-strain curves of different unidirectional composites	18
2.4	: Stress-strain curves for CF/PEEK laminates	18
2.5	: S-N curves for 1045 steel and 2014-T6 aluminium	22
2.6	: Tension-tension S-N curves for unidirectional composite	22
2.7	: Schematic representation of S-N curves	23
2.8	: Effect of stress ratio on fatigue strength of unidirectional composites, XAS/914	24
2.9	: Schematic hysteresis loops at 1 cycle and N cycles	25
2.10	: Hysteresis loop diagram, for composite under fatigue testing	27
2.11	: The three characteristic stages of damage of composites	28
2.12	: Damage mode during fatigue life	29
2.13	: Micro-level Failure Mechanism	30
2.14	: Load-controlled testing	34
2.15	: Strain-controlled testing	35
2.16	: Fluctuating tension stress cycle in sine waveform	36
2.17	: S-N curve for E-glass/913 $[(\pm 45, 0_2)_2]_s$ laminate	37
2.18	: Influence of glass content on axial fatigue strength	42
2.19	: Influence of glass content on rotating bending fatigue strength	43
2.20	: S-N curve for unidirectional graphite epoxy composite	43
2.21	: Temperature effect on fatigue strength of CFRP	44
2.22	: The influence of test frequency for waisted specimens (AS4/PEEK)	45
2.23	: Effect of reinforcement scheme on fatigue strength of CFRP	47
2.24	: Comparison of stress-life curves for three fibre composites	48

2.25	: Stress-strain curves for carbon epoxy and carbon nylon	49
2.26	: Normalised S-N data for the carbon/epoxy composites	50
2.27	: Fatigue behaviour of carbon fibre composite	51
2.28	: Effect of failure mechanisms on fatigue lives of the carbon/epoxy	52
2.29	: Tensile strength as a function of OPFB fibre loading	54
2.30	: Tensile modulus as a function of OPFB loading	55
2.31	: S-N curve of Hercules 3501-6 Epoxy at room temperature	57
3.1	: Oil palm fibre received from Sabutek (M) Sdn. Bhd	59
3.2	: Dimension of CF/epoxy composite specimen	60
3.3	: Dimension of OPFB fibre/epoxy composite specimen	61
3.4	: Straightening process	61
3.5	: OPFB fibre/epoxy composite specimens for tensile and fatigue test	63
3.6	: Instron 8500 Machine	64
3.7	: An example of stress cycle performed on CF/epoxy composite ($R = 0.1$)	65
4.1	: A bar graph of coefficient of variation	68
4.2	: A comparison of experimental CF/epoxy composite stress-strain curve with the literature	71
4.3	: Stress-strain curve of epoxy	72
4.4	: Stress-strain curves of OPFB fibre/epoxy composite	74
4.5	: A comparison of stress-strain curves for all materials	75
5.1	: Fatigue test profile of CF/epoxy composite for $R = 0.1$	78
5.2	: Fatigue test profile of OPFB fibre/epoxy composite for $R = 0.1$	78
5.3	: The S – N data for CF/epoxy composite at $R = 0.1$	80
5.4	: The S – N data for CF/epoxy composite at $R = 0.5$	80
5.5	: Stress-life curves for CF/epoxy composite	81
5.6	: Normalised stress-life diagram of CF/epoxy composite	83
5.7	: The curve-fitting line of log S-log N for CF/epoxy composite	84
5.8	: The S-N data for OPFB fibre/epoxy composite with $V_f = 35\%$, $R = 0.1$	87
5.9	: The S-N data for OPFB fibre/epoxy composite with $V_f = 35\%$, $R = 0.5$	87

5.10	: The S-N data for OPFB fibre/epoxy composite with $V_f = 55\%$, $R = 0.1$	88
5.11	: Stress-life curves for OPFB fibre/epoxy composite	89
5.12	: Normalised S-N data for OPFB fibre/epoxy composite	90
5.13	: The curve-fitting line of $\log S - \log N$ for OPFB fibre/epoxy composite	92
5.14	: A comparison of S-N curves	93
5.15	: The normalised stress-life curves as a comparison	95
5.16	: The $\log S - \log N$ diagram for CF/epoxy composite and OPFB fibre/epoxy composite	97
5.17	: The Fractured surface of CF/epoxy specimen failed in tensile test	99
5.18	: The Fractured surface of CF/epoxy specimens failed in fatigue test ($< 10^5$ cycles)	100
5.19	: The Fractured surface of CF/epoxy specimens failed in fatigue test ($> 10^5$ cycles)	101
5.20	: The gauge length section of a CF/epoxy specimen survived 10^6 cycles	101
5.21	: The fractured OPFB fibre/epoxy composite specimen after tensile test	102
5.22	: The fractured surface of OPFB fibre/epoxy composite specimens failed in tensile test ($V_f = 35\%$)	103
5.23	: The fractured surface of OPFB fibre/epoxy composite specimens failed in fatigue test ($V_f = 35\%$)	103
5.24	: The fractured surface of OPFB fibre/epoxy composite specimen failed in tensile test ($V_f = 55\%$)	104
5.25	: The fractured surface of OPFB fibre/epoxy composite specimen failed in fatigue test ($R = 0.1$, $V_f = 35\%$)	105

NOMENCLATURE

FRP	Fibre Reinforced Plastics.
EFB	Empty Fruit Bunch.
PMC	Polymer Matrix Composites.
PEEK	Poly-ether-ether-ketone.
PPS	Polyphenylene Sulfide.
CFRP	Carbon fibre reinforced plastic.
E_1, E_2, E_3	Axial moduli (principal material directions)
ν_{12}, ν_{13}	Axial Poisson's ratio.
ν_{23}	Transverse Poisson's ratio.
G_{12}, G_{13}	Axial shear moduli.
G_{23}	Transverse shear moduli.
$\epsilon_1, \epsilon_2, \epsilon_3$	Axial strain (principal material directions).
$\sigma_1, \sigma_2, \sigma_3$	Axial stress (principal material directions).
P	Force
m, f, c	Subscripts m, f, and c refer to matrix, fibre and composite respectively
W_m	Matrix weight fraction
W_f	Fibre weight fraction
W_c	Composite weight fraction
V_m	Matrix volume fraction
V_f	Fibre volume fraction
V_c	Composite volume fraction
ρ	Density.
σ_{ult}	Ultimate tensile stress.
R	Stress ratio.
S_{max}	Maximum stress level
S	Maximum applied stress
N_f	Number of cycles to failure
CF	Carbon Fibre
OPFB	Oil Palm Fruit Bunch

CHAPTER 1

INTRODUCTION

The present trend in the design of engineering components is towards using fibrous composite especially for structural applications in the aircraft and automotive industries. These industries need materials that are light in terms of weight but stiff in terms of strength, which is synonymous with composite materials. Amongst the popular form of fibres used are glass, carbon, boron and kevlar as reinforcing materials in fibre reinforced plastics (FRP), which have been widely accepted as materials for structural and non-structural applications.

In Malaysia, these fibres are generally imported in the form of woven roving, chopped strand mat and filament wind roving. However, these materials are very expensive and their use is justified only in aerospace applications. Mallick (1991) has stated one major obstacle to the widespread use of advanced composites is their costs. Therefore natural fibres like banana, cotton, sisal, coir, oil palm empty fruit bunch and jute have attracted the attention of many researchers as an alternative fibre especially for application in consumer goods, low-cost housing and other civil structures.

At the same time, the recent trend in environmental awareness has contributed to a great interest in the development, improvement and use of natural fibres as the reinforcing materials in polymeric composites. Ray *et. al* (2001) have stated that the attractive features of natural fibres are their low cost, lightweight, high specific modulus, renewability and biodegradability. Composites reinforced with such

natural fibres have been the subject of intense study for low cost application in contrast to the synthetic fibre-reinforced composites.

According to Stowell (2001) Malaysia produces 16.5 million tonnes of oil palm fruit bunch (OPFB) fibre processed in oil palm mill a year. Based on this figures, Malaysia has a great potential in turning its abundant supply of oil palm industry by-products into value-added products such as using the OPFB fibre as reinforcement or fillers in composite material. Therefore a lot of research work and studies need to be done on this to provide sufficient information of the material.

Before discussing any further about this project some understanding on several keywords such as composite, carbon fibre, oil palm fruit bunch, thermoset polymer and fatigue behaviour must be acquired. The word composite is always related to a newly developed or modern material but the fact is composites have been used since the beginning of human civilisation in the form of natural resources. Natural resources such as wood, bamboo and rattan are known as natural composite or traditional composite. The advantages obtained from these natural composites, evolved the idea of developing Artificial Composites, which are widely used nowadays.

In general composite materials are combinations of materials put together to achieve a particular function. The combinations may be materials of the same class or of different class. The fibres are the principal load-carrying members, while the surrounding matrix keeps them in the desired location and orientation, acts as a load

transfer medium between them and protects them from environmental damages due to elevated temperatures and humidity.

According to Mallick (1991), a composite material is a combination of two or more chemically different materials with a distinct interface between them. The constituent materials maintain their separate identities in the composite and their combination produces properties and characteristics that are different from those of the constituents.

Gowda *et. al* (1999) observed that, the main reason for the interest in FRP (fibre reinforced plastic) is due to their high specific modulus, high stiffness to weight ratio and high strength to weight ratio compared to conventional materials. The higher specific modulus and specific strength of composite materials means that the weight of components can be reduced. This is a factor of great importance in moving components especially in all forms of transport where reduction in weight result in greater efficiency and energy saving.

Polymer matrix composites (PMC) are fibre-reinforced polymers in which either a thermoset or a thermoplastic polymer is used as the matrix. According to Stinchcomb (1990) the development of PMCs for structural applications started in the 1950s, and they are the most common fibre-reinforced composite in use today. One reason for their growing use is that their processing method is relatively simple and does not require very high temperatures and pressures. The equipment required for processing PMCs is also relatively simple and less expensive than that required for other types of composites

The thermoplastics soften upon heating and can be reshaped with heat and pressure. Thermoplastic polymers used for composites include polypropylene, polyvinyl chloride, nylon, polyurethane, poly-ether-ether-ketone (PEEK), polyphenylene sulfide (PPS) and polysulfone. The thermoplastic composites offer the potential for the higher toughness and high volume, low cost processing. They have a useful temperature range upwards of 225°C, (Herakovich, 1998).

Thermoset polymers become cross-linked during fabrication and do not soften upon reheating. The most common thermoset polymer matrix materials are polyesters, epoxies and polyimides. Polyesters are used extensively with glass fibres. They are inexpensive, lightweight, have a useful temperature range up to 100°C and are somewhat resistant to environmental exposures. Epoxies are more expensive but have better moisture resistance and lower shrinkage on curing. They can withstand a maximum temperature in the vicinity of 175°C. Polyimides can withstand a higher temperature 300°C but are more difficult to fabricate (Herakovich, 1998).

According to Mall (1990), graphite fibres (carbon) are lighter than glass fibres, and therefore they are preferred in applications where fatigue and weight are of primary concern such as in aerospace applications. Some of the attributes of carbon fibres such as high specific strength and stiffness, low coefficient of thermal expansion and low abrasion, biological and chemical inertness, X-ray permeability, fatigue resistance, self-lubrication, high damping, high corrosion resistance, and electrical conductivity are significant in the selection of fibre as reinforcement. There are three main routes for producing carbon fibres; namely, orientation of polymer

precursor by stretching, orientation by spinning and orientation during carbonisation and graphitisation.

Oil palm fruit bunch fibre is a non-hazardous biodegradable material extracted from oil palm's vascular bundles in the empty fruit bunch through a patented (MY-304644-A) decortation process. The fibres are clean, non-carcinogenic, free from pesticides and almost free from soft parenchyma cells, (Sabutek 2002). According to Ridzuan *et. al* (2002) oil palm fruit bunch fibre can be used as filler in plastic to reduce its cost, where plastic on the other hand is increasingly expensive especially with the high petroleum price. Gowda *et. al* (1999) also found that natural fibre composites possess better electrical resistance, good thermal and acoustic insulating properties and higher resistance to fracture.

Understanding the material behaviour is fundamental to the design of new products, especially when using complex materials such as composites. There are only limited research works being carried out on oil palm fruit bunch fibre. In order to promote the use of this material, there must be sufficient information of the material especially on the mechanical properties and its fatigue behaviour. The mechanical properties and fatigue behaviour of composites can vary significantly with factors such as temperature, load rate, pre-cycling and environmental exposure, (Mallick, 1991). In order to determine the mechanical and physical properties of the material several tests should be conducted and among them are tensile, compression, bending and fatigue tests.

Hull (1981) has defined Fatigue as the ultimate failure of a material or component by the application of a varying load whose maximum amplitude, if continuously applied, is insufficient to cause failure. According to Mallick (1998), the fatigue properties of a material represent its response to cyclic loading, which is a common occurrence in many practical applications. It is well recognised that the strength of a material is significantly reduced under cyclic loads. The cycle to failure depends on a number of variables, such as stress level, stress state, mode of cycling, process history, material composition and environmental conditions. The key point is that the loads must change with time in order to have "fatigue" as described above.

The results of fatigue tests are typically presented as a plot of applied stress against number of cycles to failure. This graph is called an S-N curve as shown in Figure 1.1. This diagram is obtained by testing a number of specimens at various stress levels under certain loading conditions. The ordinate is generally the stress or strain amplitude or the maximum applied stress or strain in a cycle and is plotted on a linear scale. The abscissa is the number of cycles to failure for a fixed stress cycle and is plotted on a logarithmic scale.

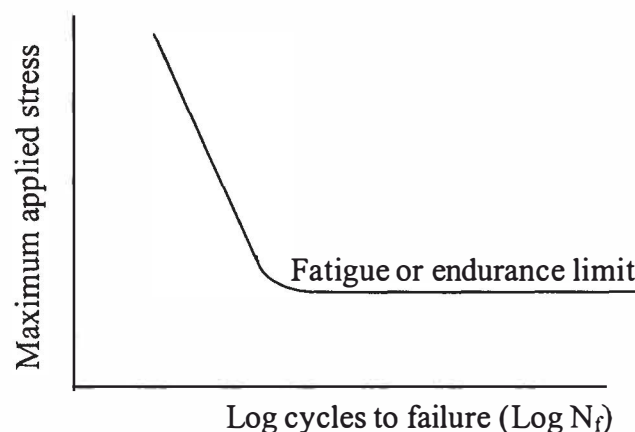


Figure 1.1: A Typical S-N curve

The damage in composites due to fatigue is limited to a range of stress. This phenomenon is known as the endurance or fatigue limit, shown schematically in Figure 1.1. The slope of the S-N curve is a measure of the resistance of the material to fatigue and the actual shape varies from one material to another. For a majority of materials, the cycle to failure increases continuously as the stress level is reduced (Mallick, 1988).

Fracture of components due to fatigue is the most common type of in service failure. Particularly in shafts, axles, aircraft wings, where cyclic stressing is taking place. This makes fatigue a widespread phenomenon in technological society nowadays, where countless devices, from the space shuttle to many children's toys, are subjected to loads whose amplitudes and forms change with time.

Fatigue failures can and often do occur under loading conditions where the fluctuating stress is below the tensile strength and, in some materials, even below the elastic limit. Because of its importance, the subject has extensively being studied over the past one hundred years but even today one still occasionally hears of the disaster in which fatigue is a prime contributing factor.

In general there are three primary fatigue analysis methods, which are usually used by researchers (Bannantine *et. al*, 1990). They are the stress-life, the strain-life and the fracture mechanics approaches. These methods have their own region of application with some degree of overlapping. The understanding of any of these methods provides a technique, which may be used to perform a fatigue analysis. However it is the insights gained from the understanding of all three methods, which